

Report of LuAG:Ce Ceramic Fibers for the RADiCAL Detector Concept

Chen Hu, *Member, IEEE*, Liyuan Zhang, *Member, IEEE*, Ren-Yuan Zhu, *Senior Member, IEEE*, Anhua Wu, Jiang Li and Liangbi Su

Abstract—HEP experiments at future hadron colliders require fast and radiation hard calorimetry. An ultra-compact RADiCAL electromagnetic calorimetry with radiation hard LYSO:Ce as active material and LuAG:Ce scintillating fibers as wavelength shifter is under development. We report an investigation on $\Phi 1$ mm LuAG:Ce ceramic fibers produced by using laser heated pedestal growth method at Shanghai Institute of Ceramics. Their photoluminescence spectra, quantum yield, and longitudinal uniformity were measured and compared to Y-11 fiber and quartz capillary wavelength shifters.

I. INTRODUCTION

AN LYSO/W/quartz capillary shashlik calorimeter has been under development in the last decade for the high luminosity large hadron collider (HL-LHC), where an absorbed dose up to 100 Mrad, a charged hadron fluence up to 6×10^{14} p/cm², and a fast neutron fluence up to 3×10^{15} n/cm² are expected. Cerium doped lutetium-aluminum garnet ceramic scintillators (Lu₃Al₅O₁₂:Ce, or LuAG:Ce) was measured to have a factor of two better radiation hardness than LYSO:Ce crystals against γ -rays, protons, and neutrons.

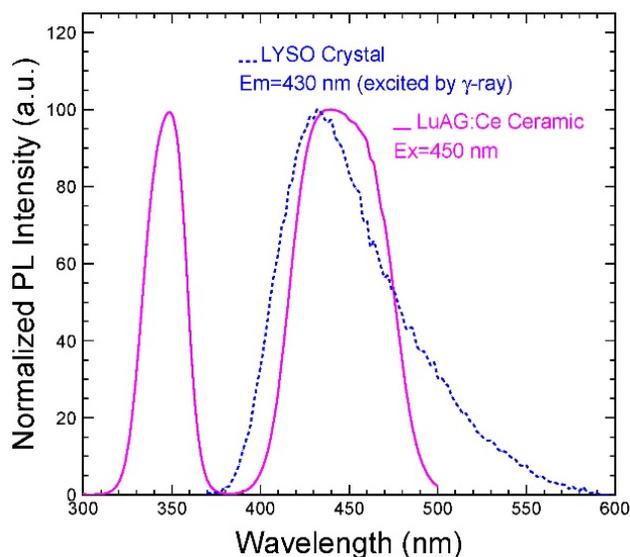


Fig. 1 LYSO emission spectra excited by γ -rays (blue dots) matches well LuAG:Ce ceramic excitation spectra (magenta lines).

Manuscript received November 14, 2021. This work was supported by the U.S. Department of Energy, Office of Science, Office of High Energy Physics, under Award Number DE-SC0011925.

C. Hu, L. Zhang, R.-Y. Zhu are with the HEP, California Institute of Technology, Pasadena, CA 91125, USA (e-mail: zhu@caltech.edu).

A. Wu, J. Li and L. Su are with the Shanghai Institute of Ceramics, Chinese Academy of Sciences, Shanghai, 200050, China.

Fig. 1 shows LYSO:Ce emission spectrum (blue dots) peaked at 430 nm matches LuAG:Ce excitation spectrum peaked at 450 nm (magenta lines), indicating that LuAG:Ce may serve as a wavelength shifter (WLS) for LYSO:Ce. LuAG:Ce WLS fibers are considered for an ultra-compact, radiation hard and fast-timing shashlik calorimetry, or RADiCAL. In addition, a short LuAG:Ce segment at the electromagnetic shower maximum may provide precision timing for electrons and photons.

We measured photoluminescence (PL) spectra, quantum yield, and longitudinal uniformity for several $\Phi 1$ mm LuAG:Ce ceramic fibers and compared them to a Y-11 WLS fiber and a quartz capillary.

II. EXPERIMENTAL DETAILS

Fig. 2 shows 11 LuAG:Ce ceramic fibers of $\Phi 1 \times 40$ mm³, 3 LuAG:Ce ceramic fibers of $\Phi 1 \times 60$ mm³, and 2 LuAG:Ce ceramic fibers of $\Phi 1 \times 120$ mm³ fabricated at Shanghai Institute of Ceramics (SIC) by using laser heated pedestal growth method.

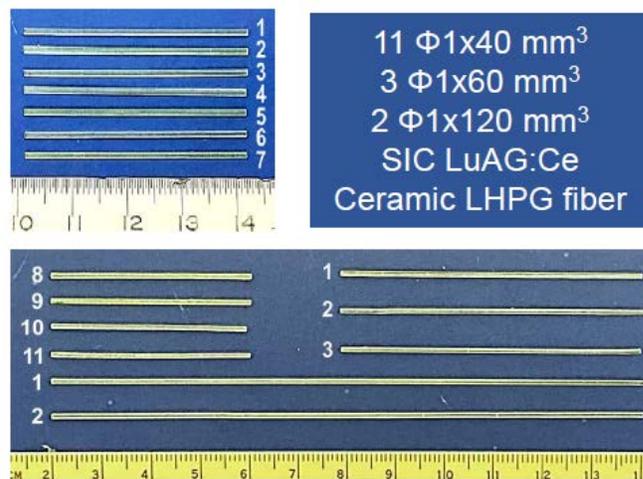


Fig. 2 11 LuAG:Ce fibers of $\Phi 1 \times 40$ mm³, 3 LuAG:Ce fibers of $\Phi 1 \times 60$ mm³, and 2 LuAG:Ce fibers of $\Phi 1 \times 120$ mm³ fabricated at SIC.

Their excitation and emission spectra were measured by using an Edinburgh spectrophotometer FLS920. An Edinburgh integrating sphere was integrated into the spectrometer and was used to measure their quantum yield with a $\Phi 1 \times 40$ mm³ quartz rod as reference. Fig. 3 shows a home-made test bench used to measure longitudinal uniformity for various WLS. The

samples were excited by a 420 nm LED at several positions. Light output was measured with two alternative ends coupled to a F4500 spectrophotometer through a $\Phi 1$ mm quartz fiber.

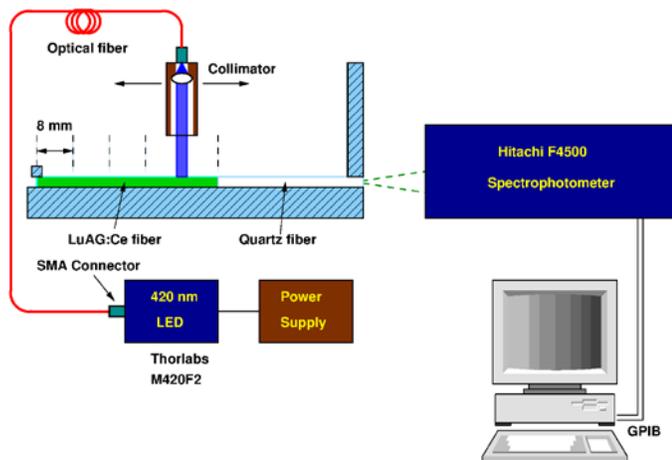


Fig. 3 A test bench used to measure longitudinal uniformity for WLS.

III. RESULTS AND DISCUSSION

Fig. 4 compares PL excitation (dashed lines) and emission (solid lines) spectra measured for a LuAG:Ce ceramic fiber (black) and a Y-11 (red) fiber of $\Phi 1 \times 40$ mm³ and a quartz capillary (blue) of $\Phi 1 \times 160$ mm³. The LuAG:Ce fiber shows a typical Ce³⁺ excitation band peaked at 445 nm, and a broad emission band from 490 to 600 nm. The PL intensity of the LuAG:Ce fiber is less than the Y-11 fiber but comparable to the quartz capillary. The LuAG:Ce PL emission intensity with 420 nm excitation (black dots) is about one third of that with 445 nm excitation (solid black line), which is consistent with the excitation spectrum shown in the plot.

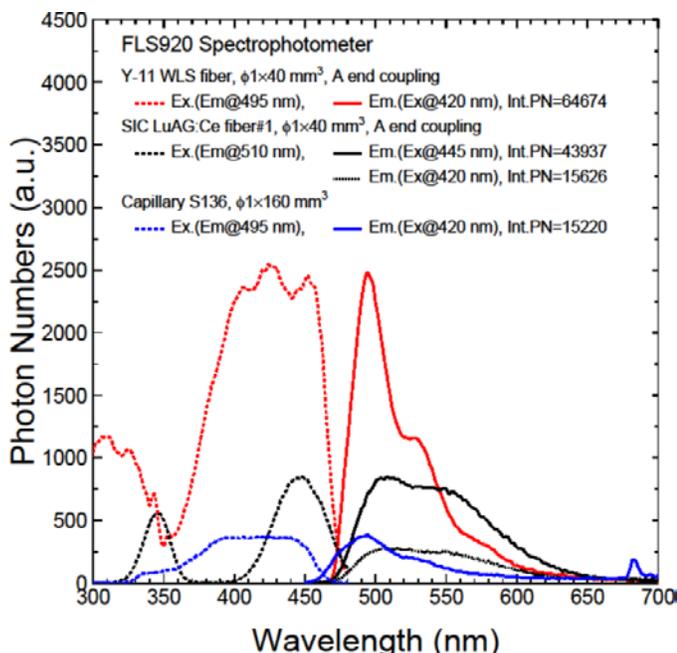


Fig. 4 PL excitation (dashes) and emission (solid) spectra are shown for a LuAG:Ce fiber (black) and a Y-11 fiber (red) of $\Phi 1 \times 40$ mm³ and a quartz capillary (blue) of $\Phi 1 \times 160$ mm³.

The quantum yield (η) of WLS was measured as 0.88 ± 0.05 for a LuAG:Ce fiber of $\Phi 1 \times 60$ mm³, which can be compared to 0.87 ± 0.05 for a Y-11 WLS fiber.

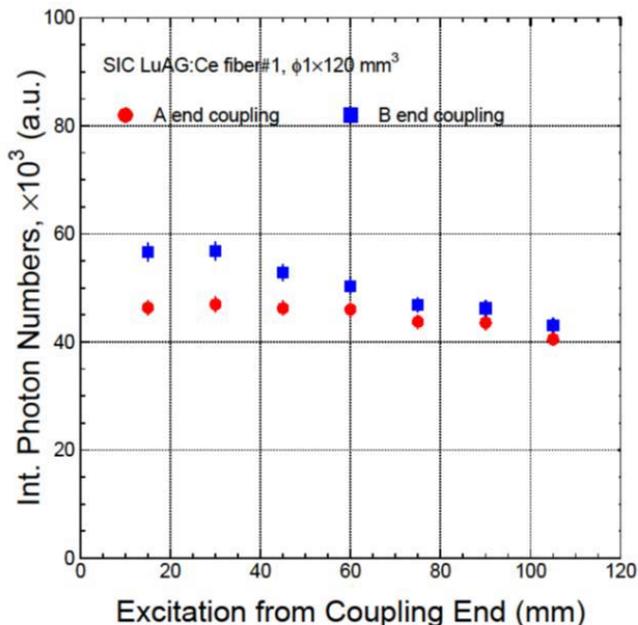


Fig. 5 Integrated PL emission photon numbers are shown as a function of the excitation position for a LuAG:Ce fiber of $\Phi 1 \times 120$ mm³ with A (red) and B (blue) end coupling.

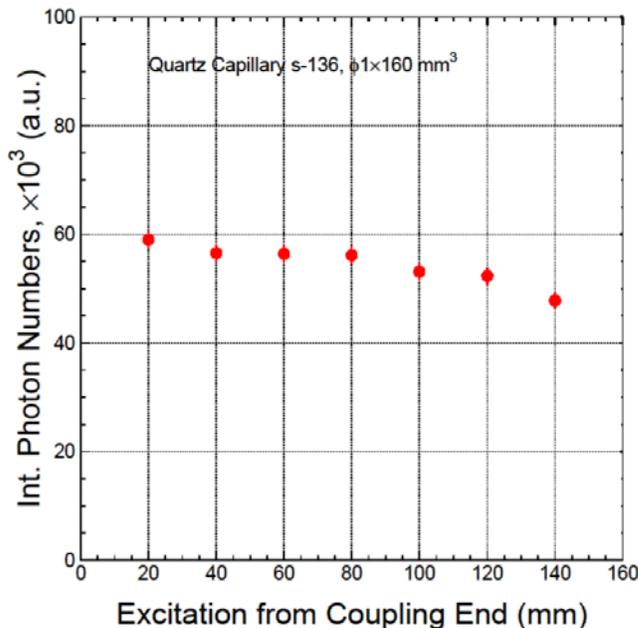


Fig. 6 Integrated PL emission photon numbers are shown as a function of the excitation position for a quartz capillary of $\Phi 1 \times 160$ mm³.

Figs. 5 and 6 show the integrated PL emission photon numbers as a function of the excitation position for a LuAG:Ce fiber of $\Phi 1 \times 120$ mm³ and a quartz capillary of $\Phi 1 \times 160$ mm³. Good intensity and uniformity were observed for the 120 mm long LuAG:Ce fiber for the A end coupling. The corresponding rms value is 5.0%, which can be compared to 6.5% for the longer quartz capillary.

IV. SUMMARY

Future HEP experiments at the HL-LHC and the proposed FCC-*hh* require fast and radiation hard calorimetry. The RADiCAL concept utilizes bright, fast and radiation hard LYSO:Ce crystals as the sensitive material and LuAG:Ce as WLS for an ultra-compact, radiation hard and fast-timing shashlik calorimeter. A total of 16 Φ 1 mm LuAG:Ce ceramic fibers of 4, 6 and 12 cm were fabricated by using Laser Heated Pedestal Growth technique at SIC. This 1st batch of LuAG:Ce WLS fibers show a quantum yield of up to 88% with light output and uniformity comparable to quartz capillary. R&D will continue to improve optical and scintillation quality of LuAG:Ce ceramic fibers.

ACKNOWLEDGEMENTS

The authors would like to thank Profs. R. Ruchti and M. Wayne for providing the Edinburgh integrating sphere and the quartz capillary used in this investigation.